



Product Guide

# Material Selection & Corrosion Guide

 **Warning**

This guide is the only document to be used in making recommendations for corrosive service for Ashcroft, Inc. products. [Call Ashcroft Stratford Customer Service for questions on unlisted chemicals or chemical concentrations.](#)

The information provided here is for general information only. [The end-user is responsible for the choice of product\(s\) in their own application, based upon their own determination of the materials, chemical, and corrosion factors involved. THIS GUIDE AND ITS CONTENT ARE PROVIDED ON AN "AS IS" BASIS WITHOUT WARRANTY OF MERCHANTABILITY AND THE WARRANTY OF FITNESS FOR A PARTICULAR PURPOSE.](#) WITHOUT LIMITING THE FOREGOING, ASHCROFT, INC., ITS DISTRIBUTORS AND SUPPLIERS MAKE NO REPRESENTATIONS OR WARRANTIES ABOUT THE ACCURACY, RELIABILITY, COMPLETENESS, OR CURRENTNESS OF THIS GUIDE AND ITS CONTENT. IN NO EVENT SHALL ASHCROFT, INC., ITS DISTRIBUTORS AND SUPPLIERS, OR ANY THIRD PARTIES MENTIONED IN THIS GUIDE BE LIABLE FOR ANY DAMAGES (INCLUDING, WITHOUT LIMITATION, INCIDENTAL AND CONSEQUENTIAL DAMAGES, PERSONAL INJURY/WRONGFUL DEATH, LOST PROFITS, OR BUSINESS LOSSES) RESULTING FROM THE USE OF OR INABILITY TO USE THIS GUIDE OR ITS CONTENT, WHETHER BASED ON WARRANTY, CONTRACT, TORT, OR ANY OTHER LEGAL THEORY, AND WHETHER OR NOT ASHCROFT, INC., ITS DISTRIBUTORS AND SUPPLIERS, OR ANY THIRD PARTIES MENTIONED IN THIS GUIDE ARE ADVISED OF THE POSSIBILITY OF SUCH DAMAGES. ANY LIABILITY OF ASHCROFT, INC., ITS DISTRIBUTORS AND SUPPLIERS, OR ANY THIRD PARTIES MENTIONED IN THIS GUIDE SHALL BE LIMITED TO ASHCROFT, INC.'S STANDARD TERMS OF SALE, WARRANTY, AND LIMITATION OF LIABILITY SHALL APPLY TO ALL SUCH SALES OR PROVISIONS OF SERVICE. PRODUCTS AND SERVICES ARE GUARANTEED TO BE FREE FROM DEFECTS IN WORKMANSHIP AND MATERIALS FOR A PERIOD OF ONE YEAR FROM THE DATE OF DELIVERY THEREOF. ASHCROFT, INC., ITS DISTRIBUTORS AND SUPPLIERS, OR ANY THIRD PARTIES MENTIONED IN THIS GUIDE ARE NOT LIABLE FOR ANY PERSONAL INJURY, INCLUDING DEATH, CAUSED BY YOUR USE OR MISUSE OF THIS GUIDE OR ITS CONTENT. ANY CLAIMS ARISING IN CONNECTION WITH YOUR USE OF THIS GUIDE AND ITS CONTENT MUST BE BROUGHT WITHIN ONE (1) YEAR OF THE DATE OF THE EVENT GIVING RISE TO SUCH ACTION OCCURRED. REMEDIES UNDER THESE TERMS AND CONDITIONS ARE EXCLUSIVE AND ARE LIMITED TO THOSE EXPRESSLY PROVIDED FOR IN THESE TERMS AND CONDITIONS.

Careless use of this table could result in an accident endangering life and property. Most process plants or refineries have chemical or corrosion engineers, who are better able to specify instrument materials since they are familiar with the details and past history of their own applications. This guide should be used only when the end-user has no such resource or additional sources of information. [Consult the Ashcroft Stratford Customer Service Department about chemicals or conditions not covered in the guide – don't guess!](#)

The table is intended to serve solely as a general guide in the recommendation of materials for corrosive services and must be regarded as indicative only and not as any guarantee for a specific service. There are many conditions that cannot be covered by a simple tabulation such as this, which is based on uncontaminated chemicals, not mixtures.

Many of the chemicals listed are dangerous or toxic. No material recommendation should be made when there is insufficient information, a high degree of risk, or an extremely dangerous chemical. The end-user is responsible for testing materials in their own application, or for securing the services of a qualified engineer to recommend materials.

## References:

This guide was developed for Ashcroft Inc. products from the manufacturer's literature and standard references such as:

*Corrosion Data Survey, Metals Section* (1985) or *Non-Metals Section* (1975), available from NACE, (National Association of Corrosion Engineers) P. O. Box 218340, Houston, TX 79231, Phone (713) 492-0535.

*Chemical Resistance Guide for Metals and Alloys, —Plastics, and —for Elastomers*, all published by Compass Publications, PO Box 2276, LaMesa, CA 91943, Phone (619) 589-9636.

*Chemical Resistance* vol II *Thermoplastic Elastomers, Thermosets and Rubbers* 2nd ed. 1994, PDL, Plastics Design Library, Morris, NY 13808.

To quote part of ASME B40.100 - 2022 Pressure Gauges and Gauge Attachments from ASME, New York, NY; Paragraph 2-3.1: Adequate safety results from intelligent planning and careful selection and installation of gauges into a pressure system. The user should inform the supplier of all conditions pertinent to the application and environment so that the supplier can recommend the most suitable gauge for the application.

The elastic element is generally a thin walled member, which operates under high stress conditions and must be carefully selected for compatibility with the pressure medium being measured. None of the common element materials are impervious to every type of chemical attack. The potential for corrosive attack is established by many factors, including the concentration, temperature and contamination of the medium.

In addition to the factors discussed above, the capability of the pressure element is influenced by the design, materials and fabrication of the joints between its parts.

## Factory Questions:

The Ashcroft Stratford Engineering or Customer Service Departments will provide assistance when necessary, but the end users engineers should always be consulted first. If Ashcroft, Inc. is to be questioned, please be prepared with the following information.

Mandatory Information	Desired Information
<ul style="list-style-type: none"> <li>• Temperature</li> <li>• Pressure</li> <li>• Concentration % of each constituent</li> </ul>	<ul style="list-style-type: none"> <li>• Impurities</li> <li>• Inhibitors Used</li> <li>• Adjacent Piping Material</li> <li>• Hazardous Location</li> </ul>

Also, the name and phone number of the facility engineer or technical contact. Be sure of the chemical name of the corrodent; seemingly minor differences in name can mean entirely different substances. For example, sodium nitrite is quite different from sodium nitrate. Cupric chloride has corrosion properties different from cuprous chloride.

## Other Gauge Selection Guidelines:

Since a Bourdon tube is a spring, it may encounter corrosion fatigue. Minimize stresses by selecting a gauge with a pressure range twice the maximum operating pressure. Specify a liquid-filled gauge with a throttle plug if there is pulsation or vibration.

To repeat ASME B40.100 in part:

2-3.2.1 Operating pressure. The pressure gauge selected should have a full-scale pressure such that the operating pressure occurs in the middle half (25% to 75%) of the scale. The full-scale pressure of the gauge selected should be approximately 2 times the intended operating pressure.

Do not use a steel Bourdon tube if the adjacent piping is a more corrosion resistant material; avoid mixing dissimilar metal alloys.

A diaphragm seal made of suitably corrosion resistant materials should be used where there is potential for corrosion of pressure elements; for clogging by solids, or abnormal temperature.

To use online Material Selection Guide tool, go to: <https://www.ashcroft.com/webtools/materialselector>

## Corrosion Guide Legend Details

O	<p>An open circle means the material is OK for the service. The uniform corrosion rate is less than .002 per year and there is no tendency for pitting or stress corrosion. A Bourdon tube, bellows, diaphragm or lower housing of this material may be used.</p> <p>An "O" under the "R" column indicates an "R" gauge system (carbon steel socket, 316 SS Bourdon tube) is permissible if the adjacent piping is iron or steel. There may be some rusting.</p>
L	<p>The letter "L" indicates the uniform corrosion rate is less than .020 inches per year and the material is suitable only for a diaphragm seal lower housing. It is NOT suitable for a Bourdon tube, bellows or diaphragm.</p>
X	<p>Cross in box indicates material is not recommended, there is insufficient information, or there are complex restrictions that cannot be addressed in this simple table. The Ashcroft Stratford Engineering Department has access to more detailed corrosion information and may be consulted if there are questions and there is no facility engineer available.</p>
★	<p>See special note in left column of this line.</p>

Observe the temperature limitations in the table for rubber and plastic components. These may be lower than temperature listed for the corrodent.

## ⚠ Oxidizing Agent Warning

The **PLUS!**™ performance option (XLL) may be used for a gauge intended for service on oxygen or an oxidizing chemical.

### Liquid Fill for Gauges and Diaphragm Seals Used with Oxidizing Agents:

Halocarbon® gauge or diaphragm seal fill is required for use with media that are strong oxidizing agents. Leakage of strong oxidizing agents may cause fires or violent reactions if mixed with glycerin, silicone, or oil instrument fills. To specify Halocarbon®, add variation XGX to the product code for gauges, or variation XCF for diaphragm seals. Any liquid may be used to fill a gauge on a diaphragm seal.

### Halocarbon® is mandatory for use with:

- \* Dry or moist - **Chlorine, Oxygen, Ozone** or **ETO** (Ethylene Oxide)
- \* With concentrated - **Sulfuric acid** or **Nitric acid**
- \* With concentrated - **Sodium Hypochlorite, Sodium Chlorate, Sodium Chlorite, Chlorine Dioxide** or **Hydrogen Peroxide**

**Less common chemicals requiring Halocarbon® include aqueous solutions, with over 10% of chemical compounds, whose name ends in any of the following:** (For example, hydrogen peroxide, sodium permanganate, potassium chlorate).

- |   |  |
|---|--|
| • Bromate                                   | • Perchlorate                          |
| • Chlorate & Chlorite                       | • Permanganate                         |
| • Chromate                                  | • Persulfate                           |
| • Hypochlorite incl.<br>Sodium Hypochlorite | • Perodate                             |
| • Dichromate                                | • Peroxide, incl.<br>Hydrogen Peroxide |
| • Nitrate & Nitrite                         | • Perselenate                          |
| • Perborate                                 |  |

## Oxidizing Agent Warning (cont.)

Halocarbon is a trademark for chlorotrifluoroethylene (CTFE) oils and greases made by Halocarbon LLC Peachtree, GA. Huntsman Advanced Materials America's Fluorolube® has the same non-reactive chemical, both carry the CAS number 9002-83-9. Chemical Abstracts Service (CAS) is a division of the American Chemical Society, that assigns a unique identifying number for each chemical compound and its structure.

Dilute water solutions (over 90% water) of these chemicals do not normally behave as oxidizing agents. The customer's facility engineer is responsible for deciding whether a solution could be hazardous.

In the following corrosion chart, chemical names with a  (Bomb Symbol) are oxidizing agents and Halocarbon® fill should be used for solutions with over 10% of the chemical.

If in doubt whether a material is an oxidant, consult the facility engineer, Ashcroft Stratford Engineering, or a reference such as Dangerous Properties of Industrial Materials, N.I. Sax, Van Nostrand Reinhold, or the U. S. Department of Transportation Hazardous Materials Table in 49CFR 172.101 the Merck Index, or other publications.

## ⚠ Sour Gas/Oil Warning

### **NACE Gauges and Pressure Products for Sour Gas or Oil Service:**

Please see ASH/PI-60 for oilfield or refinery applications requiring instruments meeting MRO175/ ISO 15156 OR NACE MRO0103. Non-metals are not yet covered by the NACE standard. Teflon™ TFE has a good rating but it is permeable. Viton™ is not recommended and the Kalrez® compound 2037 used for Ashcroft diaphragms, has poor resistance to the amine inhibitors frequently used to reduce corrosion of metals in sour oil fields.

## ⚠ Dry Chlorine/Titanium Warning

Please note that **Titanium** is not suitable when exposed to **dry chlorine** (either vapor or liquid). In the absence of water, Titanium can burn and possibly explode, even at room temperature.

Do not confuse **Titanium** with **Tantalum**.

Tantalum is fully resistant to dry or wet chlorine and is the most frequently used diaphragm material when combined with a Hastelloy® C lower housing.

Do not confuse liquid chlorine with "wet" chlorine. Wet means there is water mixed with the chlorine, which can form hydrochloric acid. Chlorine gas liquefies at about 120 psi and is normally shipped as a liquid in pressurized containers.

Chlorine is the highest volume chemical produced in the USA and is used extensively in treating both potable water and sewage treatment.

## ⚠ Hydrogen Warning

Please note that for gauge systems over 1,000 psi the entire wetted system must be Type 316 stainless steel. Transducers 5,000 psi and over must use an A-286 stainless steel sensor. For a better understanding of the hazards associated with the use of hydrogen, compatible hydrogen material and product recommendations, please refer to our "Hazards and Safe Operation of Pressure and Temperature Instruments in Hydrogen Systems" guide:

<https://sales.ashcroft.com/hydrogen-solutions-guide-lp>.

# Corrosion Data Guide

To use online Material Selection Guide tool, go to: <https://www.ashcroft.com/webtools/materialselector>

**Legend**

<b>O</b> = OK for indicated service	<b>R</b> = "R" System Permissible with Steel Piping	[ ] = Ashcroft Material Code
<b>L</b> = OK for lower housing only	 = Halocarbon® fill <b>Go to Halocarbon®</b>	> = Greater than
<b>X</b> = Unsuitable or Insufficient information		< = Less than

Corroddent	Common Names & Formulas	Corroddent Temp. °F MAX	Concentration % in H <sub>2</sub> O	Metals													Plastics				Elastomers					
				403/410 SS [SE]	Carbon Steel [B]	17-4 PH® 303/304SS, A286	316, 316L SS [S]	Carpenter 20® Cb 3 [D]	Phos. Bronze or Brass [A]	Monel® [P OR M]	Nickel [N]	Inconel® 600, 718 [W], [WW]	Hastelloy® B2 [G]	Hastelloy® C276 [H]	Tantalum [U]	Titanium [T]	"R" Systems	PVC (-40/140 °F) [V]	Kynar® (PVDF) (180 °F) [KY]	Halar® (ECTFE) (250 °F)	Teflon® (PTFE) (400 °F) [T]	EPDM (175 °F)	Viton™ (FKM) (300 °F) [Y]	Buna-N (NBR) (150 °F)	Kalrez® 2037 (FFKM) (200 °F)	
ACETIC ACID (EPDM <140 °F)		200	<40	X	X	L	O	O	X	X	X	X	X	X	O	O	O	X	X	O	O	O	O	X	X	O
ACETIC ANHYDRIDE		200	-	X	X	L	X	X	X	X	X	X	X	X	O	O	O	X	X	X	X	O	O	X	X	O
ACETONE		150	-	X	X	O	O	O	O	O	O	O	O	O	O	O	O	O	X	X	X	O	O	X	X	O
ACETYLENE, DRY (Explosive in Cu)		200	100	O	O	L	O	O	X	X	O	O	O	O	O	O	O	O	X	X	X	O	O	X	X	O
ACROLEIN		200	100	X	X	X	L	L	X	L	L	L	L	L	O	O	X	X	X	X	O	O	X	X	O	
ALUMINUM CHLORIDE	AlCl <sub>3</sub> , Polyaluminum Chloride	150	-	X	X	X	X	X	X	X	X	X	X	O	X	X	X	L	O	O	O	O	O	O	O	
ALUMINUM SULFATE	Alum. Al <sub>2</sub> (SO <sub>4</sub> ) <sub>3</sub>	150	<50	X	X	X	L	L	X	X	X	X	O	O	O	O	X	L	O	O	O	O	O	O	O	
AMMONIA ANHYDROUS (Wet, see Ammonium Hydroxide)	DOT Quality NH <sub>3</sub>	300	100	O	O	O	O	O	X	X	X	X	L	L	X	X	O	X	X	O	O	O	X	X	X	
AMMONIUM CHLORIDE	Sal Ammoniac NH <sub>4</sub> Cl	200	<40	X	X	X	X	X	X	X	X	X	X	O	O	O	X	X	O	O	O	O	O	X	O	
AMMONIUM HYDROXIDE	Ammonia Water NH <sub>3</sub> in Water	120	<30	X	X	O	O	L	X	X	X	X	L	L	X	O	X	O	O	O	O	O	X	O	O	
AMMONIUM NITRATE 	Norway Saltpeter NH <sub>4</sub> NO <sub>3</sub>	200	<50	L	X	X	O	O	X	X	X	X	X	L	O	O	O	O	O	X	O	X	X	O	O	
AMMONIUM SULFATE	(NH <sub>4</sub> ) <sub>2</sub> SO <sub>4</sub>	200	<60	X	X	X	L	L	X	X	L	X	X	L	O	O	X	O	O	O	O	O	X	O	O	
AMYL ACETATE		250	-	X	L	O	O	O	X	X	X	X	O	O	O	O	O	X	X	X	O	X	X	X	O	
ANILINE		200	>99	X	X	L	O	O	X	L	L	L	X	X	O	O	X	X	X	X	O	X	X	X	O	
ARGON (DRY)	Ar	200	>99	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	
BEER		200	-	X	X	O	O	O	X	X	X	X	X	X	X	X	X	O	O	X	O	O	X	O	X	

# Corrosion Data Guide

To use online Material Selection Guide tool, go to: <https://www.ashcroft.com/webtools/materialselector>

**Legend**

<b>O</b> = OK for indicated service	<b>R</b> = "R" System Permissible with Steel Piping	[ ] = Ashcroft Material Code
<b>L</b> = OK for lower housing only	 = Halocarbon® fill <b>Go to Halocarbon®</b>	> = Greater than
<b>X</b> = Unsuitable or Insufficient information		< = Less than

Corrodent	Common Names & Formulas	Corrodent Temp. °F MAX	Concentration % in H <sub>2</sub> O	Metals												Plastics				Elastomers					
				403/410 SS [SE]	Carbon Steel [B]	17-4 PH® 303/304SS, A286	316, 316L SS [S]	Carpenter 20® Cb 3 [D]	Phos. Bronze or Brass [A]	Monel® [P OR M]	Nickel [N]	Inconel® 600, 718 [W], [WW]	Hastelloy® B2 [G]	Hastelloy® C276 [H]	Tantalum [U]	Titanium [T]	"R" Systems	PVC (-40/140°F) [V]	Kynar® (PVDF) (180 °F) [KY]	Halar® (ECTFE) (250 °F)	Teflon™ (PTFE) (400 °F) [T]	EPDM (175 °F)	Viton™ (FKM) (300 °F) [Y]	Buna-N (NBR) (150 °F)	Kalrez® 2037 (FFKM) (200 °F)
BENZENE	C <sub>6</sub> H <sub>6</sub>	200	<50	L	L	L	O	L	O	O	O	X	X	O	O	O	X	X	X	O	X	X	X	O	
BENZIDINE		200	<99	L	L	L	L	L	L	L	L	L	L	L	O	O	X	X	X	X	X	X	X	X	O
BENZOIC ACID		200	<70	L	X	L	L	L	X	L	L	X	O	O	O	O	X	X	O	L	O	X	X	X	O
BLACK LIQUOR	Sulfate Liquor	200	-	X	X	X	X	L	X	X	X	X	X	X	X	X	X	X	X	L	O	X	O	X	X
BLEACH	<5% NaOCl	120	<5	X	X	X	X	X	X	X	X	X	X	O	O	O	X	O	O	O	O	O	O	X	O
BORIC ACID	H <sub>3</sub> BO <sub>4</sub>	150	<25	X	X	L	O	O	L	L	L	L	O	O	O	O	X	O	O	O	O	O	O	O	O
BROMINE, DRY 	Br (<57 PPM H <sub>2</sub> O)	140	>99	X	X	X	X	X	X	L	L	O	L	L	O	X	X	X	O	O	X	X	O	X	O
BROMOBENZENE		200	>99	X	X	X	O	O	X	L	L	L	L	O	O	O	O	X	X	X	O	X	O	X	O
BUTADIENE (BUTYLENE)		200	>99	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	X	O	X	X	X	O
BUTANE	C <sub>4</sub> H <sub>10</sub>	200	-	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	O	X	O	O	O
BUTYL ALCOHOL	Butanol	200	-	O	X	O	O	O	O	O	O	O	O	O	O	O	X	X	O	O	O	X	O	O	O
BUTYRIC ACID		200	<10	X	X	X	L	L	X	X	X	X	O	O	O	O	X	X	O	O	O	X	X	X	O
CALCIUM BISULFATE	Ca(HSO <sub>3</sub> ) <sub>2</sub>	250	>90	X	X	X	O	X	X	X	X	X	X	X	X	O	X	O	O	O	O	X	O	X	O
CALCIUM CHLORIDE	CaCl <sub>2</sub>	200	<80	X	X	X	X	X	X	X	X	O	O	O	O	O	X	O	O	O	O	O	O	O	O
CALCIUM HYDROXIDE	Slaked Lime Ca(OH) <sub>2</sub>	200	<50	X	X	X	L	X	X	X	X	X	X	O	O	O	X	O	O	O	O	O	O	O	O
CALCIUM HYPOCHLORITE 	Ca(OCl) <sub>2</sub>	75	<10	X	X	X	X	X	X	X	X	X	X	L	O	O	X	O	O	O	O	O	O	X	O
CARBON DIOXIDE, WET	CO <sub>2</sub>	150	-	X	X	O	O	O	X	O	X	O	O	O	O	O	X	O	O	O	O	O	O	O	O
CARBON MONOXIDE	CO	200	>99	O	O	O	O	O	O	O	X	O	O	O	O	O	O	X	O	X	O	O	O	O	O

# Corrosion Data Guide

To use online Material Selection Guide tool, go to: <https://www.ashcroft.com/webtools/materialselector>

**Legend**

- O** = OK for indicated service
- L** = OK for lower housing only
- X** = Unsuitable or Insufficient information
- R** = "R" System Permissible with Steel Piping
-  = Halocarbon® fill **Go to Halocarbon®**
- [ ] = Ashcroft Material Code
- > = Greater than
- < = Less than

Corrodent	Common Names & Formulas	Corrodent Temp. °F MAX	Concentration % in H <sub>2</sub> O	Metals													Plastics				Elastomers				
				403/410 SS [SE]	Carbon Steel [B]	17-4 PH®, 303/304SS, A286	316, 316L SS [S]	Carpenter 20® Cb 3 [D]	Phos. Bronze or Brass [A]	Monel® [P OR M]	Nickel [N]	Inconel® 600, 718 [W], [WW]	Hastelloy® B2 [G]	Hastelloy® C276 [H]	Tantalum [U]	Titanium [T]	"R" Systems	PVC (-40/140 °F) [V]	Kynar® (PVDF) (180 °F) [KY]	Halar® (ECTFE) (250 °F)	Teflon™ (PTFE) (400 °F) [T]	EPDM (175 °F)	Viton™ (FKM) (300 °F) [Y]	Buna-N (NBR) (150 °F)	Kalrez® 2037 (FFKM) (200 °F)
CHLORINATED WATER (<10ppm Chlorine)		70	<10 ppm	X	X	O	O	O	O	O	X	X	L	O	O	O	X	O	O	O	O	X	O	X	O
CHLORINATED WATER (To Saturation)		120	-	X	X	X	X	O	X	X	X	X	L	O	O	O	X	O	O	O	X	X	X	X	O
CHLORINE, DRY  (* SEE PAGE 5) (<50PPM H <sub>2</sub> O)	Cl <sub>2</sub>	200	>99	X	X	X	X	L	X	X	L	X	X	L	O	X*	X	X	L	X	X	X	O	X	O
CHLORINE, MOIST 		160	>90	X	X	X	X	X	X	X	X	X	L	O	X	X	X	L	X	X	X	X	X	X	
CHLOROACETIC ACID		150	<30	X	X	X	X	X	L	X	X	L	L	O	L	X	X	X	O	X	X	X	X	O	
CHLOROFORM, DRY	Trichloromethane CHCl <sub>3</sub>	100	>99	X	X	X	O	O	X	O	O	O	X	X	O	O	X	X	O	O	O	X	X	X	O
CHROMIC ACID	Chromium Trioxide H <sub>2</sub> CrO <sub>4</sub>	200	<30	X	X	X	X	X	X	X	X	X	X	O	O	X	X	O	O	O	X	O	X	O	
CITRIC ACID		200	>10 <50	X	X	X	O	O	X	L	L	L	O	O	O	O	X	O	O	O	O	O	O	O	O
COPPER NITRATE 	Cupric Nitrate Cu(NO <sub>3</sub> ) <sub>2</sub>	200	<10	X	X	O	O	O	X	X	X	X	X	X	O	O	X	X	O	O	O	X	O	O	O
COPPER SULFATE	Cupric Sulfate CuSO <sub>4</sub>	200	<30	X	X	X	L	O	X	X	X	X	X	O	O	O	X	O	O	O	O	O	O	O	O
CREOSOTE	Coal-Tar	200	-	X	L	L	L	L	L	L	L	L	L	O	O	X	X	X	X	X	O	X	O	X	O
CREOSOL		200	>99	O	X	X	O	O	L	O	O	O	O	O	O	L	X	X	O	X	O	X	X	X	O
CRUDE OIL - SOUR (SEE WARNING PG. 5)		<200	<5	X	X	X	X	X	X	O	X	X	X	O	O	X	X	X	O	O	O	X	X	X	X
CRUDE OIL - SWEET, LOW SULFUR		200	-	X	L	O	O	O	X	O	O	O	O	O	O	O	O	O	O	O	O	X	O	X	O
CUPRIC CHLORIDE	Copper Chloride	200	<40	X	X	X	X	X	X	X	X	X	X	O	O	X	O	O	O	O	O	O	O	O	
DIESEL FUEL		140	-	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	O
DOWTHERM A		300	-	O	O	O	O	O	X	O	O	O	O	O	O	O	O	X	X	X	O	X	X	X	O
ETHANOL	Ethyl Alcohol C <sub>2</sub> H <sub>5</sub> OH	200	-	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O

# Corrosion Data Guide

To use online Material Selection Guide tool, go to: <https://www.ashcroft.com/webtools/materialselector>

## Legend

<b>O</b> = OK for indicated service	<b>R</b> = "R" System Permissible with Steel Piping	[ ] = Ashcroft Material Code
<b>L</b> = OK for lower housing only	= Halocarbon® fill <b>Go to Halocarbon®</b>	> = Greater than
<b>X</b> = Unsuitable or Insufficient information		< = Less than

Corrodent	Common Names & Formulas	Corrodent Temp. °F MAX	Concentration % in H <sub>2</sub> O	Metals													Plastics				Elastomers						
				403/410 SS [SE]	Carbon Steel [B]	17-4 PH® , 303/304SS, A286	316, 316L SS [S]	Carpenter 20® Cb 3 [D]	Phos. Bronze or Brass [A]	Monel® [P OR M]	Nickel [N]	Inconel® 600,718 [W], [WW]	Hastelloy® B2 [G]	Hastelloy® C276 [H]	Tantalum [U]	Titanium [T]	"R" Systems	PVC (-40/140 °F) [V]	Kynar® (PVDF) (180 °F) [KY]	Halar® (ECTFE) (250 °F)	Teflon™ (PTFE) (400 °F) [T]	EPDM (175 °F)	Viton™ (FKM) (300 °F) [Y]	Buna-N (NBR) (150 °F)	Kalrez® 2037 (FFKM) (200 °F)		
ETHANOL AMINES	MEA, DEA, TEA	120	100	X	L	O	O	O	X	O	L	L	O	O	O	O	O	O	X	X	X	O	O	X	X	X	X
ETHYL ACETATE		<200	-	X	L	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	X	X	O	X	X	X	O
ETHYL CHLORIDE, DRY	Chloroethane	<200	>99	O	O	X	X	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	O	X	O	O	O
ETHYLENE	Ethene	200	-	O	O	O	O	O	O	O	X	O	O	O	O	O	O	X	O	X	X	O	X	X	X	O	
ETHYLENE GLYCOL	Glycol	200	>40	X	X	O	O	O	L	L	L	L	O	O	O	O	O	O	O	O	O	O	O	O	O	O	
ETHYLENE OXIDE	ETO	100	>99	X	O	O	O	O	O	O	O	O	X	X	O	X	O	X	O	X	O	O	X	X	X	O	
FERRIC CHLORIDE (*VITON <170 °F)	FeCl <sub>3</sub>	200	<40	X	X	X	X	X	X	X	X	X	X	X	X	O	O	O	X	O	O	O	O	O <sup>+</sup>	O	O	
FERRIC SULFATE (*VITON <170 °F)	Fe <sub>2</sub> (SO <sub>4</sub> ) <sub>3</sub>	150	<10	X	X	X	O	O	X	X	X	O	X	O	O	O	O	X	O	O	O	O	O	O <sup>+</sup>	O	O	
FERROUS CHLORIDE (*VITON <170 °F)	FeCl <sub>2</sub>	200	<30	X	X	X	X	X	X	X	X	X	X	X	L	O	O	X	O	O	O	O	O	O <sup>+</sup>	O	O	
FERROUS SULFATE (*VITON <170 °F)	FeSO <sub>4</sub>	200	<50	X	X	X	X	L	X	X	X	X	L	L	O	O	X	O	O	O	O	O	O	O <sup>+</sup>	O	O	
FLUORINE, GAS DRY No Air or O <sub>2</sub>	F <sub>2</sub>	200	>99	X	X	X	X	X	X	O	O	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
FLUOROSILICIC ACID	Hydrofluosilicic Acid - H <sub>2</sub> SiF <sub>6</sub>	140	<30	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	O	O	O	
FORMALDEHYDE		125	-	X	X	O	O	O	X	O	O	O	L	X	O	O	X	X	X	X	O	O	X	X	X	O	
FORMIC ACID		<150	-	X	X	X	X	X	X	X	X	X	L	L	O	X	X	X	X	X	O	O	O	X	X	O	
FUEL OIL, LIGHT	Diesel, No. 2, Heating Oil	140	-	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	
FUEL OIL, HEAVY	Bunker, Resid, No. 6, Heavy Gas Oil	300	-	X	X	X	L	O	X	X	X	X	X	X	O	O	O	X	X	X	O	X	O	O	O		
FURFURAL		200	<10	X	X	O	X	O	L	L	L	X	L	O	O	L	X	X	X	X	O	O	X	X	X	O	
GASOLINE (*FLOWING-PHOS BRONZE)		200	-	X	X	O	O	X	L	X	X	L	O	O	O	X	X	X	X	X	O	O	X	O	O		
GLUCOSE		300	-	X	X	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	O	O	O	O		



# Corrosion Data Guide

To use online Material Selection Guide tool, go to: <https://www.ashcroft.com/webtools/materialselector>

## Legend

- O** = OK for indicated service
- L** = OK for lower housing only
- X** = Unsuitable or Insufficient information
- R** = "R" System Permissible with Steel Piping
-  = Halocarbon® fill **Go to Halocarbon®**
- [ ] = Ashcroft Material Code
- > = Greater than
- < = Less than

Corrodent	Common Names & Formulas	Corrodent Temp. °F MAX	Concentration % in H <sub>2</sub> O	Metals													Plastics				Elastomers											
				403/410 SS [SE]	Carbon Steel [B]	17-4 PH®, 303/304SS, A286	316, 316L SS [S]	Carpenter 20® Cb 3 [D]	Phos. Bronze or Brass [A]	Monel® [P OR M]	Nickel [N]	Inconel® 600,718 [W], [WW]	Hastelloy® B2 [G]	Hastelloy® C276 [H]	Tantalum [U]	Titanium [T]	"R" Systems	PVC (-40/140 °F) [V]	Kynar® (PVDF) (180 °F) [K Y]	Halar® (ECTFE) (250 °F)	Teflon™ (PTFE) (400 °F) [T]	EPDM (175 °F)	Viton™ (FKM) (300 °F) [V]	Buna-N (NBR) (150 °F)	Kalrez® 2037 (FFKM) (200 °F)							
NAPHTHA	Benzin	200	>99	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	O	
NAPHTHALENE	Tar Camphor C <sub>10</sub> H <sub>8</sub>	150	>99	O	O	O	O	O	L	O	O	O	X	X	L	O	O	X	O	X	O	X	O	X	O	X	O	X	O	X	O	
NATURAL GAS, DOT QUALITY (* Cu alloy <100PSI)		150	-	X	L	O	O	X	O*	L	X	X	X	X	O	O	O	X	O	X	O	X	O	X	O	X	O	X	O	X	O	
NICKEL CHLORIDE	NiCl <sub>2</sub>	200	<80	X	X	X	X	X	X	X	X	X	X	X	O	O	O	O	X	O	O	O	O	X	O	O	O	O	O	O	O	
NICKEL SULFATE	NiSO <sub>4</sub>	200	-	X	X	X	O	L	X	X	X	X	X	X	X	X	X	O	X	L	O	O	O	O	O	O	O	O	O	O	O	
NITRIC ACID 	HNO <sub>3</sub>	<100	<95	X	X	O	O	O	X	X	X	X	X	X	X	O	X	X	X	O	O	O	O	X	X	X	X	X	X	X	X	
NITROGEN (DRY)		200	>99	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	
NITROUS OXIDE (DRY)	Laughing Gas N <sub>2</sub> O	<100	>99	X	X	X	L	L	X	X	X	X	X	X	L	O	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
N-METHYLPYRROLIDONE	NMP	70	>99	X	X	X	L	O	X	X	O	O	O	O	X	X	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
OLEIC ACID		200	-	X	X	X	L	O	L	L	L	O	L	L	O	L	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
OXALIC ACID		140	<50	X	X	X	X	X	X	X	X	X	X	L	O	X	X	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O
OXYGEN GAS ("XGB") 	O <sub>2</sub>	120	-	X	X	O	O	O	O	O	X	O	O	O	O	X	X	X	X	X	O	O	X	X	X	X	X	X	X	X	X	
OZONE 	O <sub>3</sub>	120	<8	X	X	O	O	O	X	X	X	X	X	X	X	X	X	X	X	X	O	O	X	X	X	X	X	X	X	X	X	
PALMITIC ACID		160	>99	X	X	O	O	X	X	X	X	X	X	X	O	X	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
PHENOL		120	>90	X	X	O	O	O	X	L	O	O	X	O	O	X	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
PHOSPHORIC ACID	H <sub>3</sub> PO <sub>4</sub>	100	<60	X	X	X	O	O	X	X	X	L	O	O	O	X	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
PHTHALIC ANHYDRIDE		200	>99	X	O	X	O	O	X	O	O	O	O	O	O	O	X	O	O	O	O	O	X	O	O	O	O	O	O	O	O	
PICRIC ACID		200	<10	X	X	X	O	X	X	X	X	X	X	L	O	X	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
POTASSIUM CHLORIDE	KCl	150	<30	X	X	X	X	X	X	L	L	X	L	O	O	O	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
POTASSIUM HYDROXIDE	KOH	160	<50	X	L	X	L	L	X	O	O	L	L	L	X	X	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
POTASSIUM NITRATE 	Salt peter KNO <sub>3</sub>	200	<50	L	L	X	L	X	L	L	L	L	X	L	O	O	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	
POTASSIUM NITRITE 	KNO <sub>2</sub>	200	<50	L	L	X	L	L	L	L	L	L	L	L	X	X	X	X	X	X	O	O	X	X	X	X	O	X	X	O	O	

# Corrosion Data Guide

To use online Material Selection Guide tool, go to: <https://www.ashcroft.com/webtools/materialselector>

## Legend

<b>O</b> = OK for indicated service	<b>R</b> = "R" System Permissible with Steel Piping	[ ] = Ashcroft Material Code
<b>L</b> = OK for lower housing only	= Halocarbon® fill <b>Go to Halocarbon®</b>	> = Greater than
<b>X</b> = Unsuitable or Insufficient information		< = Less than

Corrodent	Common Names & Formulas	Corrodent Temp. °F MAX	Concentration % in H <sub>2</sub> O	Metals													Plastics				Elastomers				
				403/410 SS [SE]	Carbon Steel [B]	17-4 PH® 303/304SS, A286	316, 316L SS [S]	Carpenter 20® Cb 3 [D]	Phos. Bronze or Brass [A]	Monel® [P OR M]	Nickel [N]	Inconel® 600, 718 [W], [MW]	Hastelloy® B2 [G]	Hastelloy® C276 [H]	Tantalum [U]	Titanium [T]	"R" Systems	PVC (-40/140 °F) [V]	Kynar® (PVDF) (180 °F) [KY]	Halar® (ECTFE) (250 °F)	Teflon™ (PTFE) (400 °F) [T]	EPDM (175 °F)	Viton™ (FKM) (300 °F) [Y]	Buna-N (NBR) (150 °F)	Kalrez® 2037 (FFKM) (200 °F)
POTASSIUM PERMANGANATE	KMnO <sub>4</sub>	140	<30	X	X	X	X	X	X	X	X	X	X	X	O	O	X	X	O	O	O	O	X	X	O
PROPANE	C <sub>3</sub> H <sub>8</sub>	200	>99	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	O
PROPYLENE		200	>99	O	O	O	O	O	O	O	O	O	O	O	O	X	O	X	O	X	O	X	O	X	O
ROSIN		200	-	X	X	O	O	O	L	O	O	X	X	O	X	X	O	X	X	X	O	X	X	O	O
SEA WATER (* Monel® not for Diaphragms)	Ocean Water	200	-	X	X	X	X	X	O*	X	O	X	O	O	O	X	O	O	O	O	O	O	O	O	
SEWAGE, RAW		100	-	X	X	X	L	L	L	L	X	X	X	O	O	X	X	O	O	O	O	X	O	O	O
SILICONE OIL	PDMS	140	-	O	O	O	O	O	O	O	O	O	O	O	O	O	L	O	O	O	O	O	O	O	
SILVER NITRATE (Acid free)	AgNO <sub>3</sub>	200	<50	L	X	X	L	O	X	X	X	X	X	X	O	X	X	O	O	O	O	O	O	X	O
SKYDROL		200	100	X	X	O	O	O	X	O	O	O	O	O	O	X	X	X	X	X	O	O	X	X	O
SODIUM BICARBONATE	Baking Soda NaHCO <sub>3</sub>	<200	<20	O	L	O	O	O	L	O	O	O	L	L	X	O	O	O	O	O	O	O	O	O	O
SODIUM BISULFATE	NaHSO <sub>4</sub>	<200	<30	X	X	X	X	O	L	L	L	X	L	L	O	X	X	O	O	O	O	O	O	X	O
SODIUM BISULFITE	NaHSO <sub>3</sub>	<150	<40	X	X	X	X	L	X	L	X	X	L	L	O	O	X	O	O	O	O	O	O	O	O
SODIUM CARBONATE	Soda Ash Na <sub>2</sub> CO <sub>3</sub>	<200	<40	O	L	O	O	O	X	O	O	O	O	O	O	X	O	O	O	O	O	O	O	O	
SODIUM CHLORIDE	Table Salt NaCl	<200	<30	X	X	X	X	X	O	L	O	X	O	O	O	X	O	O	O	O	O	O	O	O	
SODIUM CHROMATE	Na <sub>2</sub> CrO <sub>4</sub>	<200	<60	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	X	O	O	
SODIUM CYANIDE	NaCN	<140	-	X	O	O	O	O	X	X	X	X	X	X	O	O	O	O	O	O	O	O	O	O	O
SODIUM DICHROMATE	S. Bichromate Na <sub>2</sub> Cr <sub>2</sub> O <sub>7</sub>	<140	<20	O	L	O	O	O	X	X	X	X	X	X	X	O	O	O	O	O	O	O	O	X	O
SODIUM FLUORIDE		<140	<20	X	X	X	X	X	O	X	X	X	L	X	O	X	O	O	O	O	O	O	X	O	
SODIUM HYDROXIDE	Caustic Soda NaOH	<150	<40	X	X	O	O	O	L	O	O	O	O	O	X	O	O	O	X	O	O	O	X	O	O
SODIUM HYDROXIDE	Caustic Soda NaOH	<200	<70	X	X	X	X	O	X	O	O	O	O	L	X	X	X	X	X	X	O	O	X	X	O

# Corrosion Data Guide

To use online Material Selection Guide tool, go to: <https://www.ashcroft.com/webtools/materialselector>

**Legend**

<b>O</b> = OK for indicated service	<b>R</b> = "R" System Permissible with Steel Piping	[ ] = Ashcroft Material Code
<b>L</b> = OK for lower housing only	= Halocarbon® fill <a href="#">Go to Halocarbon®</a>	> = Greater than
<b>X</b> = Unsuitable or Insufficient information		< = Less than

Corrodent	Common Names & Formulas	Corrodent Temp. °F MAX	Concentration % in H <sub>2</sub> O	Metals											Plastics				Elastomers									
				403/410 SS [SE]	Carbon Steel [B]	17-4 PH®, 303/304SS, A286	316, 316L SS [S]	Carpenter 20® Cb 3 [D]	Phos. Bronze or Brass [A]	Monel® [P, OF M]	Nickel [N]	Inconel® 600, 718 [W], [MW]	Hastelloy® B2 [G]	Hastelloy® C276 [H]	Tantalum [U]	Titanium [T]	"R" Systems	PVC (-40/140 °F) [M]	Kynar® (PVDF) (180 °F) [KY]	Halar® (ECTFE) (250 °F)	Teflon® (PTFE) (400 °F) [T]	EPDM (175 °F)	Viton™ (FKM) (300 °F) [Y]	Buna-N (NBR) (150 °F)	Kalrez® 2037 (FFKM) (200 °F)			
SODIUM HYPOCHLORITE  (*Kynar 15% max. conc.)	NaOCl, Bleach	120	<40	X	X	X	X	X	X	X	X	X	X	X	O	O	X	O	X	O	X	O	O	X	O	X	O	
SODIUM NITRATE	Chile Saltpeter NaNO <sub>3</sub>	<200	-	O	L	O	O	O	X	X	O	X	X	X	O	O	O	O	O	O	O	O	O	O	O	X	X	O
SODIUM NITRITE	NaNO <sub>2</sub>	<200	<60	O	O	O	O	O	X	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X
SODIUM PERMANGANATE  (pH >6, no chlorides)	NaMnO <sub>4</sub>	<120	<50	X	X	X	O	O	X	X	O	X	X	X	O	O	O	X	X	O	X	O	X	O	O	X	O	
SODIUM PEROXIDE	Na <sub>2</sub> O <sub>2</sub>	<200	<10	O	L	O	O	O	X	L	L	L	L	L	X	X	O	L	O	O	O	O	O	O	O	X	O	
SODIUM PHOSPHATE (TRIBASIC)	TSP Na <sub>3</sub> PO <sub>4</sub>	<200	<60	O	O	O	O	O	O	O	O	O	O	L	O	O	X	O	O	O	O	O	O	O	O	X	O	
SODIUM SILICATE	Water Glass	<200	-	O	O	O	O	O	X	O	O	O	X	L	O	O	O	O	O	O	O	O	O	O	O	O	O	O
SODIUM SULFATE	Na <sub>2</sub> SO <sub>4</sub>	<200	<30	O	X	L	O	O	L	L	L	L	L	L	O	O	O	O	O	O	O	O	O	O	O	O	O	O
SODIUM SULFIDE	Na <sub>2</sub> S	<200	<30	X	X	X	L	O	X	L	L	L	X	L	O	X	X	O	O	O	O	O	O	O	O	X	O	O
SODIUM SULFITE (*Viton<140 °F)	Na <sub>2</sub> SO <sub>3</sub>	<200	<30	X	X	X	O	O	X	X	X	X	X	O	O	O	O	O	O	O	O	O	O	O	O	O*	X	O
SODIUM THIOSULFATE	Na <sub>2</sub> S <sub>2</sub> O <sub>3</sub>	<200	-	X	X	X	O	O	X	O	L	L	L	L	O	X	X	O	O	O	O	O	O	O	O	O	X	O
SOUR GAS / OIL (SEE WARNING PG. 5)		<200	<5	X	X	X	X	X	X	O	X	X	X	O	O	X	X	O	O	O	O	O	O	O	X	X	X	X
STANNOUS CHLORIDE	Tin Dichloride SnCl <sub>2</sub>	<200	<50	X	X	X	X	L	X	X	X	X	X	X	O	X	X	X	O	X	O	O	O	O	O	O	O	O
STEAM (WITH SIPHON)		<300	-	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	X	X

# Corrosion Data Guide

To use online Material Selection Guide tool, go to: <https://www.ashcroft.com/webtools/materialselector>


**Legend**

<b>O</b> = OK for indicated service	<b>R</b> = "R" System Permissible with Steel Piping	[ ] = Ashcroft Material Code
<b>L</b> = OK for lower housing only	 = Halocarbon® fill <a href="#">Go to Halocarbon®</a>	> = Greater than
<b>X</b> = Unsuitable or Insufficient information		< = Less than

Corrodent	Common Names & Formulas	Corrodent Temp. °F MAX	Concentration % in H <sub>2</sub> O	Metals													Plastics				Elastomers				
				403/410 SS [SE]	Carbon Steel [B]	17-4 PH®, 303/304SS, A286	316, 316L SS [S]	Carpenter 20® Cb 3 [D]	Phos. Bronze or Brass [A]	Monel® [P OR M]	Nickel [N]	Inconel® 600,718 [W], [WW]	Hastelloy® B2 [G]	Hastelloy® C276 [H]	Tantalum [U]	Titanium [T]	"R" Systems	PVC (-40/140 °F) [V]	Kynar® (PVDF) (180 °F) [KY]	Halar® (ECTFE) (250 °F)	Teflon™ (PTFE) (400 °F) [T]	EPDM (175 °F)	Viton™ (FKM) (300 °F) [Y]	Buna-N (NBR) (150 °F)	Kalrez® 2037 (FFKM) (200 °F)
STEARIC ACID		<200	-	X	X	O	O	O	X	X	O	L	X	O	O	X	X	O	O	O	O	X	X	X	O
STODDARD SOLVENT		<150	-	O	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	O	X	O	O	O
SULFAMIC ACID		<150	<95	X	X	X	X	X	X	X	X	X	L	O	X	X	X	O	X	O	O	X	X	O	
SULFUR	S	250	>95	X	X	X	X	X	X	X	O	L	O	O	O	X	X	X	X	O	O	O	X	O	
SULFUR DIOXIDE, WET	SO <sub>2</sub>	140	-	X	X	X	L	X	X	X	X	X	L	O	O	X	X	L	O	O	O	O	X	O	
SULFUR HEXAFLUORIDE	SF <sub>6</sub>	120	-	O	O	O	O	O	O	O	O	O	O	O	O	O	L	X	X	O	O	X	X	X	
SULFUR TRIOXIDE, DRY	SO <sub>3</sub>	140	>99	X	X	X	L	L	X	X	L	L	X	O	X	X	O	X	X	O	O	O	X	O	
SULFURIC ACID <60%	H <sub>2</sub> SO <sub>4</sub>	200	<60	X	X	X	X	X	X	X	X	X	L	X	O	X	X	O	O	O	O	X	X	O	
SULFURIC ACID 80-98%	H <sub>2</sub> SO <sub>4</sub>	200	<98	X	X	X	X	X	X	X	X	X	L	X	O	X	X	X	O	O	X	X	X	O	
TANNIC ACID	Tannin	<150	-	X	O	L	O	O	X	O	X	L	X	X	O	O	O	O	O	O	O	O	O	O	
TARTARIC ACID		<150	<50	X	X	X	O	X	X	O	X	O	X	X	O	X	X	O	O	O	O	O	O	O	
TOLUENE	Toluol	<200	>99	O	O	O	O	O	O	O	O	O	O	O	O	O	X	X	X	O	X	X	X	O	
TRICHLOROACETIC ACID		<200	<50	X	X	X	X	X	X	L	X	X	L	O	X	X	X	X	X	X	X	X	X	O	
TRICHLOROETHANE 1,1,1, DRY (* Teflon <200 °F)		<150	>98	O	O	O	O	O	O	O	O	O	O	O	O	O	X	X	X	O*	X	X	X	O	
TRICHLOROETHYLENE, DRY		<200	>99	X	O	O	O	O	X	O	O	L	O	O	O	O	X	O	X	O	X	X	X	O	
TURPENTINE		<200	>98	O	O	O	O	O	O	O	O	O	O	O	O	L	X	O	O	O	X	O	X	O	
UREA	Carbamide, DEF	<200	<50	X	X	O	O	X	X	X	X	L	X	X	X	O	X	O	O	O	O	X	X	X	
VINYL CHLORIDE		<100	>99	X	X	X	O	O	X	O	X	X	X	O	O	X	X	O	X	O	X	X	X	O	
XYLENE		<150	-	O	O	O	O	O	O	O	O	O	O	O	O	O	X	O	O	X	X	O	X	O	



Learn more about Ashcroft instrumentation  
by visiting our website:

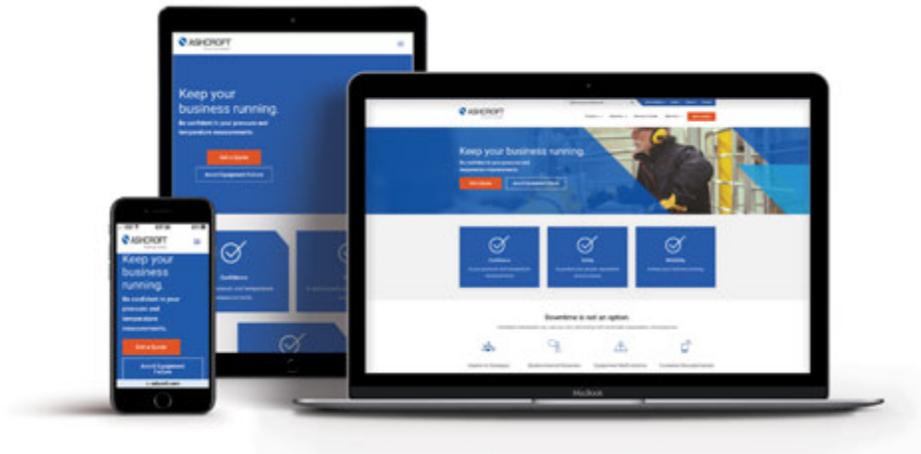

[ashcroft.com](https://www.ashcroft.com)

**Keep your critical equipment and processes  
running with confidence.**

Process, industrial and manufacturing companies need quality pressure and temperature measurements to keep their critical equipment and processes running. Understanding that your business can't stop, Ashcroft designs and manufactures reliable instrumentation to meet the most challenging applications worldwide so you can confidently run your business.

For more information about pressure and temperature measurement solutions, please [contact us](#) to discuss your specific requirements.

All specifications are subject to change without notice. All sales subject to standard terms and conditions.

Ashcroft® and Trust the Shield® are trademarks of Ashcroft Inc. The following non-Ashcroft trademarks are the property of their respective owners: 17-4 PH®, Carpenter 20®, Halar®, Hastelloy®, Inconel®, Kalrez®, Kynar®, Monel®, Teflon™, Viton™.

For more information, see [Ashcroft Brands & Trademarks](#) ©2024 Ashcroft Inc. corrosion\_guide\_pg\_RevB\_04-02-24

 **ASHCROFT®**  
Trust the shield.®

[ashcroft.com](https://www.ashcroft.com) | 1.800.328.8258 | [Contact Us](#)